

Microtensile Bond Strength of Composite to Enamel Using Universal Adhesive with/without Acid Etching Compared To Etch and Rinse and Self-Etch Bonding Agents

Hoda Pouyanfar¹, Elaheh Seyed Tabaii², Samaneh Aghazadeh³, Seyyed Pedram Tabatabaei Navaei Nobari⁴, Mohammad Moslem Imani⁵

¹Department of Restorative Dentistry, Dental Faculty, Kermanshah University of Medical Sciences, Kermanshah, Iran; ²Orthodontic Department, Qom University of Medical Sciences, Qom, Iran; ³Private Practice, Tehran, Iran; ⁴Students Research Committee, Kermanshah University of Medical Sciences, Kermanshah, Iran; ⁵Department of Orthodontics, Kermanshah University of Medical Sciences, Kermanshah, Iran

Abstract

Citation: Pouyanfar H, Seyed Tabaii E, Aghazadeh S, Tabatabaei Navaei Nobari SP, Imani MM. Microtensile Bond Strength Of Composite To Enamel Using Universal Adhesive With/Without Acid Etching Compared To Etch And Rinse And Self-Etch Bonding Agents. Open Access Maced J Med Sci. 2018 Nov 25; 6(11):2186-2192. <https://doi.org/10.3889/oamjms.2018.427>

Keywords: Tensile Strength; Dental Adhesives; Acid Etching, Dental; Composite Resins

***Correspondence:** Mohammad Moslem Imani, Department of Orthodontics, Kermanshah University of Medical Sciences, Kermanshah, Iran. E-mail: mmoslem.imani@yahoo.com

Received: 17-Aug-2018; **Revised:** 20-Oct-2018; **Accepted:** 22-Oct-2018; **Online first:** 22-Nov-2018

Copyright: © 2018 Hoda Pouyanfar, Elaheh Seyed Tabaii, Samaneh Aghazadeh, Seyyed Pedram Tabatabaei Navaei Nobari, Mohammad Moslem Imani. This is an open-access article distributed under the terms of the Creative Commons Attribution-NonCommercial 4.0 International License (CC BY-NC 4.0)

Funding: This research was financially supported by the Research Council of Kermanshah University of Medical Sciences (Grant number: 95381)

Competing Interests: The authors have declared that no competing interests exist

AIM: Considering the recent introduction of universal adhesives and the controversy regarding the use/no use of etchant prior to their application, this study sought to assess the microtensile bond strength of composite to enamel using universal adhesive with/without acid etching compared to three-step etch and rinse, two-step etch and rinse and two-step self-etch bonding agents.

METHODS: This in vitro, an experimental study was conducted on 80 extracted sound human molars in five groups (16 each): Scotchbond Universal adhesive (3M) with/without prior etching, Adper Scetche otchbond Multi-Purpose, Single Bond and Clearfil SE Bond. Etching was performed with 37% phosphoric acid for 20 seconds followed by rinsing and drying. The bonding agent was then applied and light-cured. The e-lite composite was bonded to surfaces and light-cured. The teeth were then mounted, sectioned and subjected to microtensile bond strength test in a universal testing machine. The mode of failure was, determined under a stereomicroscope. Data were analysed using one-way ANOVA followed by Tukey's test.

RESULTS: Universal adhesive with prior etching yielded the highest bond strength ($P = 0.03$). Pairwise comparisons showed that the bond strength of this group was significantly higher than that of universal adhesive without prior etching ($P = 0.04$). No other significant differences were noted ($P > 0.05$). The modes of failure were significantly different among the groups ($P = 0.003$).

CONCLUSION: Enamel etching with phosphoric acid can significantly increase the bond strength to universal adhesive. Universal adhesive without prior etching provided the bond strength as high as that provided by etching and rinse and self-etch bonding agents.

Introduction

At present, dental adhesive systems are highly popular among dental clinicians due to their ability to bond to enamel and dentin and enabling conservative cavity preparation. The composition of dental adhesive systems undergoes constant development, and new products are continuously introduced to the market [1] [2]. Bonding to enamel is easier, stronger and more durable than that to dentin due to higher mineral content and lower water content

of the enamel compared to dentin [3]. Achieving a strong and durable bonding between the restoration and tooth structure is a prerequisite for a successful restoration [3]. On the other hand, bond failure at the tooth-restoration interface causes marginal discolouration, postoperative tooth hypersensitivity, secondary caries and pulp involvement [4] [5]. The mechanism of bonding of dental adhesive systems to the dental substrate is mainly based on the replacement of the lost minerals with resin monomers, resulting in a micromechanical interlocking of polymer in dental substrate [6]. Bonding agents mediate the

bonding of composite to enamel and dentin. Resin bond to enamel is durable and predictable and is based on penetration of resin monomers into microscopic porosities of the enamel surface caused by acid etching and subsequent formation of resin tags [7]. To increase the bond strength to the dental substrate, some modifications have been made in dental adhesives regarding their chemical composition, mechanism of bonding, number of bottles (treatment steps) and their application technique, which affect their clinical efficacy. As a result, several generations of bonding agents are now available in the dental market. The two-step etches and rinses bonding agents include two steps of acid etching and application of bonding agent. In this generation of bonding agents, the primer and bonding agent are supplied together in one bottle [8]. Demand for simplification of adhesive application resulted in the development of self-etch adhesives. The two-step self-etch adhesives do not require a separate etching step and contain advanced acidic monomers such as 4-META and 10-MDP, which confer further hydrophilicity to these adhesives compared to previous generations.

To ensure the etching capability of monomers, water is also present as an ionising agent in the composition of self-etch adhesives [9]. In two-step, self-etch adhesives, etching and priming of dentin and enamel are performed simultaneously (due to the use of acidic primers). These systems have greatly simplified the adhesive application process since they do not require rinsing and drying. As a result, the risk of over-drying or excessive moisture is no longer present [8] [10] [11]. The major superiority of the 7th generation dentin bonding agents over the 6th generation is their single-step application. These bonding agents have one-step application to minimise technical sensitivity, further facilitate the bonding process and prevent the problems related to incomplete penetration of resin tags into the porosities created by etching. As a result, these systems are extremely easy to use and save time [10].

Universal adhesives are used in dentistry in self-etch, etch and rinse or selective etching modes. They can bond to methacrylate-based restorative materials, cement, sealants, dentin, enamel, glass-ionomer and indirect restoration substrates including metals, alumina, zirconia and other ceramics. They all contain acidic monomers and have a similar application pattern as that of self-etch systems. On the other hand, nano-adhesives contain nano-fillers and can form a very strong bond to dentin and enamel. Bonding systems containing nano-fillers are known as universal systems and are applied in self-etch mode. Some studies have compared different generations of bonding agents and have reported controversial results [12] [13] [14]. The quality of bonding of coronal restoration to tooth structure depends on the type of bonding agent used.

Considering the recent introduction of universal adhesives and the controversy regarding the use/no use of etchant prior to their application with regard to their bond strength, this study aimed to assess the microtensile bond strength of enamel to composite following the application of a universal adhesive with/without prior acid etching, a three-step etch and rinse bonding agent, a two-step etch and rinse bonding agent and a two-step self-etch bonding agent.

Material and Methods

This *in vitro*, an experimental study was performed on 80 extracted sound human molars. The study was approved in the Ethics Committee of Kermanshah University of Medical Sciences (Code: KUMS.REC.1395.426). Minimum sample size was calculated to be 16 in each of the five groups according to a study by Joseph et al. [15], assuming the mean bond strength of 3.35 ± 1.58 MPa for two-step self-etch adhesive and 34.93 ± 2.54 MPa for universal adhesive with 95% confidence interval and 90% study power using PASS version 21.0 software (a total of 80 samples). A total of 80 permanent sound molars extracted within the past 6 months for reasons unrelated to this study were selected using convenience sampling. The teeth were immersed in 0.5% chloramine T solution at room temperature for one week for disinfection. The teeth were then stored in distilled water at room temperature until the experiment [16]. The teeth were inspected under a light microscope to ensure the absence of caries and cracks. The teeth were randomly divided into five groups ($n = 16$) as follows:

Group 1: The buccal/labial enamel surface was etched with 37% phosphoric acid gel (Ultradent, South Jordan, UT, USA) for 20 seconds followed by 10 seconds of rinsing with water spray and 5 seconds of drying with air spray. Adper Scotchbond Multi-Purpose (3M ESPE, St. Paul, MN, USA) primer was applied on the surface, and after gentle air spray, Adper Scotchbond Multi-Purpose bonding agent was applied. Light curing was performed using a LED light curing unit (Demetron, Kerr, Orange, CA, USA) with a light intensity of 700 mW/cm^2 . Before curing, the output power of light curing unit was calibrated using a radiometer. Elite AA composite (Bisco Dental Products, Schaumburg, IL, USA) was then applied in two 2.5 mm-thick increments, and each layer was polymerized for 20 seconds. A mould measuring $9 \times 9 \times 5$ mm was used to standardize the composite thickness in this group.

Group 2: Enamel surface was etched, rinsed and dried as explained in group 1. Single Bond (3M ESPE, St. Paul, MN, USA) bonding agent was then applied in two layers and cured using a LED light

curing unit. Elite AA composite (Bisco Dental Products, Schaumburg, IL, USA) was then applied in two 2.5 mm-thick increments, and each layer was polymerized for 20 seconds. A mould measuring 9 x 9 x 5 mm was used to standardise the composite thickness.

Group 3: Two layers of Clearfil SE Bond primer were first applied on the enamel surface and dried with gentle air spray for 5 seconds. One layer of Clearfil SE Bond bonding agent was then applied on the surface and cured using a LED light curing unit. Elite AA composite (Bisco Dental Products, Schaumburg, IL, USA) was applied in two 2.5 mm-thick increments, and each layer was polymerised for 20 seconds. A mould measuring 9 x 9 x 5 mm was used to standardise the composite thickness.

Group 4: Scotchbond Universal adhesive (3M ESPE, St. Paul, MN, USA) was applied on the surface of samples without etching and cured using a LED light curing unit. Elite AA composite (Bisco Dental Products, Schaumburg, IL, USA) was applied in two 2.5 mm-thick increments, and each layer was polymerised for 20 seconds. A mould measuring 9 x 9 x 5 mm was used to standardise the composite thickness.

Group 5: The enamel surface was first etched with 37% phosphoric acid gel, and then Scotchbond Universal adhesive (3M ESPE, St. Paul, MN, USA) was applied and cured using a LED light curing unit. Elite AA composite (Bisco Dental Products, Schaumburg, IL, USA) was applied in two 2.5 mm-thick increments, and each layer was polymerised for 20 seconds. A mould measuring 9 x 9 x 5 mm was used to standardise the composite thickness.

Table 1 shows the composition of adhesives used in this study. The teeth in each group were mounted in acrylic resin perpendicular to the horizon and parallel to each other and composite was subsequently bonded to them as described earlier. After immersion in distilled water at room temperature for 24 hours, the teeth were sectioned into slices measuring 1 x 1 mm with 8 mm height by a low-speed diamond disc of a microtome (Isomet, Buehler Ltd., Bluff, IL, USA) such that the disc was perpendicular to the tooth surface. The sections of each group were separately immersed in distilled water and incubated at 37°C and 100% humidity for 24 hours.

Table 1: Composition of adhesives used in this study

| Adhesive | Composition |
|---|--|
| Clearfil SE Bond (Kuraray, Tokyo, Japan) | Primer: water, MDP, HEMA, CQ, DET, hydrophilic DMA Bond: MDP, bis-GMA, HEMA, hydrophobic DMA, CQ, DET, silanated colloidal silica |
| Adper Scotchbond Multi-Purpose (3M ESPE, St. Paul, MN, USA) | 10-MDP methacrylate resin, HEMA, Ethanol, Water, Polyacrylic Acid Copolymer, Silane, Fillers, Initiators |
| Single Bond Universal Adhesive (3M ESPE, St. Paul, MN, USA) | Adhesive: MDP phosphate monomer, methacrylate resins, HEMA, silane methacrylate-modified polyalkenoic acid copolymer, filler, ethanol, water, initiators |
| Scotchbond Universal adhesive 3M | MDP, bis-GMA, HEMA, ethanol, water, initiators |
| MDPB: 12-methacryloyloxydodecylpyridinium bromide; bis-GMA: bisphenol A diglycidylmethacrylate; HEMA: 2-hydroxyethyl methacrylate; MDP: 10-methacryloyloxydecyl; dihydrogen phosphate; DMA: dimethacrylate; DET: N,N-diethanol p-toluidine; CQ: camphorquinone. | |

For measurement of microtensile bond strength, each sample was fixed to the plate of a universal testing machine (Z020, Zwick GmbH & Co. KG, Germany) using cyanoacrylate glue. The load was applied at a crosshead speed of 0.5 mm/minute until failure. The load at failure was recorded in Newtons (N).

The interface area of the broken piece was measured by a gauge. The load at failure in Newtons was divided by the enamel/composite interface area in square millimetres (mm²) to obtain the bond strength in megapascals (MPa).

The samples were then inspected under a stereomicroscope (Olympus, SZX9, Iran) at (x 10) magnification to determine the mode of failure. The mode of failure was classified into three groups of cohesive within the tooth structure, cohesive within the composite and mixed (Figure 1).

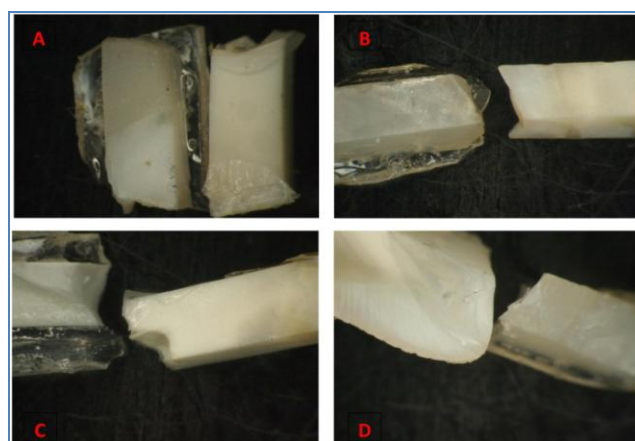


Figure 1: A) Cohesive failure in tooth structure in a universal adhesive group with an etchant; B) cohesive failure of the composite in a universal adhesive group with an etchant; C) cohesive failure of the composite in the universal adhesive group without etchant; D) cohesive failure in tooth structure in the universal adhesive group without etchant

Data were analysed using SPSS version 21 (SPSS Inc., IL, USA). Normal distribution of data was assessed using the Shapiro-Wilk test. Homogeneity of variances was assessed using the Levene's test. One-way ANOVA was applied to assess the difference in microtensile bond strength of the groups. Pairwise comparisons were carried out using Tukey's test. The modes of failure were compared among the groups using the chi-square test. $P < 0.05$ was considered significant.

Results

According to the Shapiro-Wilk test, the microtensile bond strength data were normally distributed ($P > 0.05$). The assumption of homogeneity

of variances according to the Levene's test was met ($P = 0.17$).

Maximum microtensile bond strength was obtained by the use of universal adhesive after etching while the minimum microtensile bond strength was noted in the use of universal adhesive without etchant (Table 2). According to one-way ANOVA, the difference in microtensile bond strength of the groups was significant ($P = 0.03$).

Table 2: Mean microtensile bond strength in the five groups (n=16)

| Bonding agent | Mean | Standard deviation | Minimum | Maximum | Median |
|---|---------|--------------------|---------|---------|--------|
| Scotchbond Universal 3M with etchant | 65.75b | 32.13 | 20.8 | 134.8 | 60.1 |
| Adper Scotchbond 3M | 45.81ab | 19.82 | 15.07 | 84.3 | 41.85 |
| Single Bond 3M | 45.52ab | 21.84 | 10.2 | 79.5 | 45.45 |
| Clearfil SE Bond | 44.91ab | 15.92 | 23.3 | 76.7 | 46.65 |
| Scotchbond Universal 3M without etchant | 42.75a | 19.79 | 11.16 | 80.0 | 38.6 |

Mean values with lowercase letters indicate no significant difference in pairwise comparisons.

Thus, Tukey's test was applied for pairwise comparisons (Table 3) and showed that only the difference in microtensile bond strength of universal adhesive with the etchant and universal adhesive without etchant was significant ($P = 0.04$). No other significant differences were noted in pairwise comparisons ($P > 0.05$).

Table 3: Pairwise comparison of groups regarding microtensile bond strength

| First bonding agent | Second bonding agent | Mean difference | P-value |
|------------------------------------|------------------------------------|-----------------|---------|
| Single Bond 3M | Clearfil SE Bond | 0.61 | 1.0 |
| | Universal adhesive with an etchant | 20.23 | 0.09 |
| | Universal adhesive without etchant | 2.77 | 0.99 |
| Clearfil SE Bond | Adper Scotchbond | 0.29 | 1.0 |
| | Universal adhesive with an etchant | 20.84 | 0.07 |
| | Universal adhesive without etchant | 2.16 | 0.99 |
| Universal adhesive with an etchant | Adper Scotchbond | 0.91 | 1.0 |
| | Universal adhesive without etchant | 22.99 | 0.04 |
| | Adper Scotchbond | 19.93 | 0.09 |
| Universal adhesive without etchant | Adper Scotchbond | 3.06 | 0.99 |

According to the chi-square test, the difference in modes of failure among the groups was significant ($P = 0.003$) such that cohesive failure within the composite had a significantly higher frequency in Clearfil SE Bond and universal adhesive without etchant groups while cohesive failure in tooth had a higher frequency in universal adhesive with etchant and Scotchbond groups (Table 4).

Table 4: Frequency of the modes of failure in the groups

| Mode of failure | Universal adhesive with an etchant | Scotchbond | Single Bond | Clearfil SE Bond | Universal adhesive without etchant |
|-----------------|------------------------------------|------------|-------------|------------------|------------------------------------|
| In tooth | 9 (56.3%) | 9 (56.3%) | 8 (50.0%) | 0 | 4 (25.0%) |
| In composite | 7 (43.8%) | 7 (43.8%) | 8 (50.0%) | 16 (100%) | 12 (75.0%) |

The frequency of fractures in teeth and composite was the same in the Single Bond group (Figure 2).

Discussion

This study assessed the microtensile bond strength of enamel to composite following the use of a universal adhesive with/without prior etching, three-step etch and rinse (Scotchbond), a two-step etch and rinse (Single Bond) and two-step self-etch (Clearfil SE Bond) bonding agents. The results showed that the microtensile bond strength was significantly higher in the universal adhesive with prior etching group (65.75 MPa).

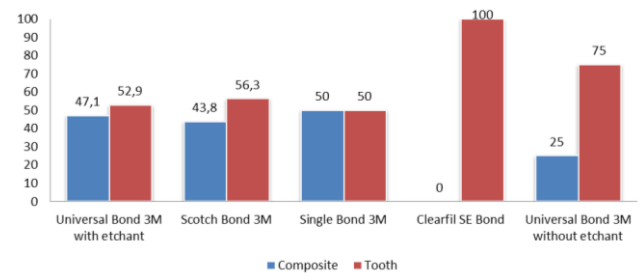


Figure 2: Frequency percentage of different modes of failure in the five groups

Pairwise comparisons showed that this group had a significant difference with universal adhesive without prior etching group. No other significant differences were noted in the bond strength among the groups. The results showed that enamel etching with phosphoric acid before the application of universal adhesive significantly increased the bond strength of enamel to composite (compared to other groups), which indicates that acid etching before the application of different bonding agents is still an acceptable method to increase the bond strength of enamel to composite. On the other hand, a universal adhesive with no prior enamel etching yielded the bond strength as high as that provided by three-step etch and rinse, a two-step etches and rinse and two-step self-etch systems. This indicates that despite the elimination of the etching step, universal adhesive yielded the bond strength as high as that of other systems.

Acid etching is a commonly used method to roughen the enamel surface and increase the bond strength of adhesive materials to enamel. Significantly higher bond strength in the universal adhesive with prior acid etching group is probably due to the formation of porosities in the enamel surface and penetration of resin into the porosities. Evidence shows that resin tags can be as long as 15-20 μ at the resin-acid etched enamel interface [17] [18]. On the

other hand, evidence shows that acid etching creates a honeycomb pattern in the enamel surfaces, which results in micromechanical retention [19]. Acid etching removes about 10 μ from the enamel surface and creates a 5-50 μ m thick porous layer [19].

On the other hand, application of self-etch adhesives on the enamel is associated with some concerns [20] [21]. The superficial etching pattern of the enamel and reduction of micromechanical retention can negatively affect the bond strength and durability [22]. Also, it is not known whether application of self-etch adhesives with moderate pH on the enamel can provide adequate mechanical and chemical resistance in the oral environment as do the etch and rinse adhesives. Further investigations are warranted to answer this question.

In line with our study, van Landuyt et al., [23] indicated that enamel surface preparation by acid etching significantly increases the bond strength. However, it has been reported that acid etching decreases the bond strength to dentin [24]. New self-etch adhesives are mainly categorised as mildly acidic adhesives, and enamel preparation by acid etching before their application can significantly increase their bond strength [25]. Thus, it should be noted that simplifying the process of adhesive application by eliminating the etch and rinse steps (as in universal adhesives) although enhances the bonding process, does not necessarily result in higher clinical success rate. Further studies are required to elucidate this topic better.

Joseph et al., [15] compared the microtensile bond strength of Clearfil SE Bond two-step self-etch adhesive, Adper Easy One 7th generation bonding agent and Futurabond universal adhesive and reported that universal adhesive had the highest bond strength followed by the two-step self-etch bonding agent. The 7th generation bonding agent ranked last regarding the bond strength. This finding was in agreement with our results since universal adhesive with prior etching yielded the highest bond strength in our study.

On the other hand, Souza-Saroni et al., [26] evaluated the microtensile bond strength of Clearfil Liner Bond 2V, Prime and Bond NT/NRC, Single Bond and All Bond 2 to enamel and reported that they all provided almost similar bond strength values. In our study, all adhesives yielded equal bond strength values to enamel except for universal adhesive with prior etching. High bond strength provided by universal adhesive can be due to the presence of nano-size cross-linkers in its composition. Clearfil SE Bond had high bond strength close to that of other groups (except for universal adhesive with prior etching). This can be due to the presence of 10-MDP in its composition, which enhances its chemical bond to hydroxyapatite crystals [27].

Clearfil SE Bond is a two-step self-etch adhesive with a mildly acidic pH (1.8). Some authors

consider it as the gold standard for self-etch adhesives [28]. Two-step self-etch adhesives such as Clearfil SE Bond have separate bottles for resin and primer and therefore are more hydrophobic. Thus, they can provide high bond strength in contrast to one-step self-etch adhesives. Favourable in vitro and clinical results related to the application of this adhesive can be attributed to its double bonding mechanism. Its mild pH can result in the formation of a micromechanical bond by creating a thin and uniform hybrid layer. It can resist debonding forces and shear loads applied during shear bond strength testing. It contains 10-MDP functional monomer and can, therefore, form a stable chemical bond with hydroxyapatite. It is resistant to hydrolytic degradation and seals the restoration margins for a long period [29].

Single Bond is a two-step etch and rinse adhesive that provided the bond strength as high as that of other groups in our study. It contains polymerising resin monomers dissolved in acetone or ethanol. It is reportedly suitable for bonding to enamel [30], and our results confirmed this statement.

Formulation of adhesive systems plays an important role in the performance and clinical service of dental materials. Universal and self-etch adhesives are generally less acidic and therefore have lower efficacy for demineralisation of the mineral phase of enamel and subsequent provision of micromechanical retention [31]. Type and amount of solvent and composition and percentage of monomers in adhesive systems as well as thinning agents can all affect the bond strength. The amount of filler and percentage of mass load are also variable in different bonding agents. The manufacturers do not disclose the exact composition of their products. Moreover, information regarding the rate of shrinkage and hardness of adhesives after polymerisation is limited [25].

Universal adhesive with/without prior acid etching was used in this study. Universal adhesives are self-etch and dual-core and have a pH of 2.2 to 3.2. Generally, self-etch universal adhesives with mild or very mild etching capability may not be able to provide adequately high bond strength to enamel [32]. Despite some concerns in this regard, the bond strength of universal adhesives has been reported to be acceptably high [33]. Our results suggested selective etching of enamel with phosphoric acid to increase the bond strength of the universal adhesive to enamel. This has also been suggested by another study [32]. However, some concerns exist in this respect. For example, the risk of excessive etching of dentin still exists due to the inability to precisely control the area and subsequent reduction of the bond strength to dentin [33].

Evidence shows that bond strength to enamel or dentin more than 20 MPa results in mainly cohesive failure in the dental substrate or composite [9] [34]. In our study, all failures were within the composite or

tooth. In Clearfil SE Bond, all fractures were within the composite and only in Scotchbond group, the percentage of fractures in tooth structure was slightly higher than that within the composite.

In the present study, the bond strength was measured using microtensile bond strength test. Application of microtensile load results in better stress distribution at the adhesive interface compared to conventional tensile or shear loads and yields more accurate results with less diversity [35] [36].

This test enables better stress distribution due to the smaller interface area, which was 1 mm² in our study. However, the bond strength tests, in general, are only suitable for ranking of adhesives because many factors such as masticatory loads, pH alterations and thermal changes are present in the oral environment and affect the bond strength of adhesives to tooth structure. Thus, the results of bond strength tests in vitro cannot well predict the performance of adhesives in the clinical setting [37]. Clinical studies are required to cast a final judgment in this regard. Also, the bond strength of different adhesives to dentin should be compared in future studies.

In conclusion, within the limitations of this study, the results showed that phosphoric acid etching of the enamel before the application of universal adhesive yielded the bond strength significantly higher than that of other groups. Universal adhesive without prior etching yielded the bond strength as high as that of two-step etch and rinse and two-step self-etch bonding agents. This finding highlights the optimal efficacy of universal adhesive in the provision of optimal bond strength with the simplified application.

Acknowledgement

The authors gratefully acknowledge the Research Council of Kermanshah University of Medical Sciences (Grant number: 95381) for the financial support. This work was performed in partial fulfilment of the requirements for the degree of general dentistry by "Seyyed Pedram Tabatabaei Navaei Nobari" at Faculty of Dentistry, Kermanshah University of Medical Sciences, Kermanshah, Iran.

Author's contribution

HP and MMI conceptualised this study, designed the methodology for data collection, collected and analysed the data, and wrote the manuscript. EST and SA extensively supported the

development of the study concept, data analysis, and the writing, editing and finalising of the manuscript. SPTNN assisted in data entry and analysis. All authors read and approved the final manuscript.

References

1. Nunes MF, Swift EJ, Perdigao J. Effects of the adhesive composition on microtensile bond strength to human dentin. *Am J Dent.* 2001; 14(6):340-3. PMID:11949791
2. Frankenberger R, Predigao J, BT Rosa, M Lopes. No bottle vs multi-bottle dentin adhesives – a microtensile bond strength and morphological study. *Dent Mater.* 2001; 17(5):373-80. [https://doi.org/10.1016/S0109-5641\(00\)00084-1](https://doi.org/10.1016/S0109-5641(00)00084-1)
3. Swift EJ, Perdigao J. Bonding to enamel & dentin a brief history & state of the art. *Quintessence Int.* 1995; 26(2):95-110. PMID:7568728
4. Yoshikawa T, Sano H, Burrow MF, Tagami J, Pashley DH. Effects of dentin depth and cavity configuration on bond strength. *J Dent Res.* 1999; 78(4):898-905. <https://doi.org/10.1177/00220345990780041001> PMID:10326734
5. Armstrong SR, Keller JC, Boyer DB. Mode of failure in the dentin-adhesive resin composite bonded joint as determined by strength based (MTBs) and fracture-based (CNSB) mechanical testing. *Dent Mater.* 2001; 17(3):201-10. [https://doi.org/10.1016/S0109-5641\(00\)00070-1](https://doi.org/10.1016/S0109-5641(00)00070-1)
6. Nakabayashi N, Kojima K, Masuhara E. The promotion of adhesion by the infiltration of monomers into tooth substrates. *J Biomed Mater Res.* 1982; 16(3):265-73. <https://doi.org/10.1002/jbm.820160307> PMID:7085687
7. Kimochi T, Yoshiyama M, Urayama A, Matsuo T. Adhesion of new commercial self-etching/self-priming bonding resin to human caries-infected dentin. *Dent Mater.* 1999; 18(4):437-43. <https://doi.org/10.4012/dmj.18.437>
8. Robbins JW, Hilton TJ, Schwartz RS, dos Santos Jr J. *Fundamentals of operative dentistry: a contemporary approach.* Summitt JB, editor. Quintessence Pub.; 2006.
9. Van Meerbeek B, De Munck J, Yoshida Y, Inoue S, Vargas M, Vijay P, Van Landuyt K, Lambrechts P, Vanherle G. Buonocore memorial lecture. Adhesion to enamel and dentin: current status and future challenges. *Oper Dent.* 2003; 28(3):215-35. PMID:12760693
10. Roberson T, Heymann H, Swift E, Sturdevant C. Chap5. *Sturdevant's art and science of operative dentistry.* 4th Ed. Mosby Co., 2002:263-97.
11. Peumans M, Kanumilli P, De Munck J, Van Landuyt K, Lambrechts P, Van Meerbeek B. Clinical effectiveness of contemporary adhesives: A systematic review of current clinical trials. *Dent Mater J.* 2005; 21(9):864-81. <https://doi.org/10.1016/j.dental.2005.02.003> PMID:16009415
12. Powers JM, Farah JW. Technique sensitivity in bonding to enamel and dentin. *Compend Contin Educ Dent.* 2010; 31 (Spec No 3):1-8; quiz 9. PMID:21053440
13. Ishikawa A, Shimada Y, Foxton RM, Tagami J. Micro-tensile and micro-shear bond strengths of current self-etch adhesives to enamel and dentin. *Am J Dent.* 2007; 20(3):161-6. PMID:17672257
14. McDonough WG, Antonucci JM, He J, Shimada Y, Chiang MY, Schumacher GE, et al. A micro shear test to measure bond strengths of dentin-polymer interfaces. *Biomaterials.* 2002; 23(17):3603-8. [https://doi.org/10.1016/S0142-9612\(02\)00089-3](https://doi.org/10.1016/S0142-9612(02)00089-3)
15. Joseph P, Yadav C, Satheesh K, Rahna R. Comparative evaluation of the bonding efficacy of sixth, seventh and eighth generation bonding agents: an in vitro study. *Int Res J Pharm.* 2013; 4(9):143-9.

16. Munoz MA, Luque I, Hass V, Reis A, Loguercio AD, Bombarda NHC. Immediate bonding properties of universal adhesive to dentine. *J Dent.* 2013; 41(5):404-11. <https://doi.org/10.1016/j.jdent.2013.03.001> PMID:23499568
17. Gwinnett AJ, Marsui A. A study of enamel adhesives. The physical relationship between enamel and adhesive. *Arch Oral Biol.* 1967; 12:1615. [https://doi.org/10.1016/0003-9969\(67\)90195-1](https://doi.org/10.1016/0003-9969(67)90195-1)
18. Buonocore MG, Matsui A, Gwinnett AH. Penetration of resin dental materials into enamel with reference to bonding. *Arch Oral Biol.* 1968; 13(1):61-70. [https://doi.org/10.1016/0003-9969\(68\)90037-X](https://doi.org/10.1016/0003-9969(68)90037-X)
19. Sharpe AN. Influence of crystal orientation in human enamel on its reactivity to acid as shown by high resolution microradiography. *Arch Oral Biol.* 1967; 12(5):583. [https://doi.org/10.1016/0003-9969\(67\)90077-5](https://doi.org/10.1016/0003-9969(67)90077-5)
20. Tay FR, Pashley DH, King NM, Carvalho RM, Tsai J, Lai SC, et al. Aggressiveness of self-etch adhesives on unground enamel. *Oper Dent.* 2004; 29(3):309-16. PMID:15195732
21. Pashley DH, Tay FR. Aggressiveness of contemporary self-etching adhesives. Part II: etching effects on unground enamel. *Dent Mater.* 2001; 17(5):430-44. [https://doi.org/10.1016/S0109-5641\(00\)00104-4](https://doi.org/10.1016/S0109-5641(00)00104-4)
22. Miyazaki M, Sato M, Onose H. Durability of enamel bond strength of simplified bonding systems. *Oper Dent.* 2000; 25(2):75-80. PMID:11203803
23. Van Landuyt KL, Kanumilli P, De Munck J, Peumans M, Lambrechts P, Van Meerbeek B. Bond strength of a mild self-etch adhesive with and without prior acid-etching. *J Dent.* 2006; 34(1):77-85. <https://doi.org/10.1016/j.jdent.2005.04.001> PMID:15979226
24. Erhardt MC, Cavalcante LM, Pimenta LA. Influence of phosphoric acid pretreatment on self-etching bond strengths. *J Esthet Restor Dent.* 2004; 16(1):33-40. <https://doi.org/10.1111/j.1708-8240.2004.tb00448.x> PMID:15259541
25. Yaseen SM, Subba Reddy VV. Comparative evaluation of shear bond strength of two self-etching adhesives (sixth and seventh generation) on dentin of primary and permanent teeth: An in vitro study. *J Indian Soc Pedod Prevent Dent.* 2009; 27(1):33-8. <https://doi.org/10.4103/0970-4388.50814> PMID:19414972
26. Souza-Zaroni WC, Seixas LC, Ciccone-Nogueira JC, Chimello DT, Palma-Dibb RG. Tensile bond strength of different adhesive systems to enamel and dentin. *Braz Dent J.* 2007; 18(2):124-8. <https://doi.org/10.1590/S0103-64402007000200007>
27. Yoshida Y, Nagakane K, Fukuda R, Nakayama Y, Okazaki M, Shintani H, et al. Comparative study on adhesive performance of functional monomers. *J Dent Res.* 2004; 83(6):454-8. <https://doi.org/10.1177/154405910408300604> PMID:15153451
28. Sarr M, Kane Aw, Vreven J, Mine A, Van Lanudyt KL, Peumans M. Micro-tensile bond strength and interfacial characterization of contemporary adhesives bonded to bur cut dentin. *Oper Dent.* 2010; 35(1):94-104. <https://doi.org/10.2341/09-076-L> PMID:20166416
29. Abdalla AL, El Zohairy AA, Abdel Mohsen MM, Feilzard AJ. Bond efficacy and interface morphology of self-etching adhesives to ground enamel. *J Adhes Dent.* 2010; 12(1):19-25. PMID:20155226
30. Swift E, Perdigo J, Heymann H. Enamel bond strengths of one-bottle adhesives. *Pediatr Dent.* 1998; 20:256-262.
31. Pashley DH, Tay FR, Breschi L, Tjaderhane L, Carvalho RM, Carrilho M, et al. State of the art of etch-and-rinse adhesives. *Dent Mater.* 2011; 27(1):1-16. <https://doi.org/10.1016/j.dental.2010.10.016> PMID:21112620 PMID:PMC3857593
32. Hanabusa M, Mine A, Kuboki T, Momoi Y, Van Ende A, Van Meerbeek B, et al. Bonding effectiveness of a new 'multi-mode' adhesive to enamel and dentine. *J Dent.* 2012; 40(6):475-84. <https://doi.org/10.1016/j.jdent.2012.02.012> PMID:22381614
33. Mena-Serrano A, Kose C, De Paula EA, Tay LY, Reis A, Loguercio AD, et al. A new universal simplified adhesive: 6-month clinical evaluation. *J Esthet Restor Dent.* 2013; 25(1):55-69. <https://doi.org/10.1111/jerd.12005> PMID:23374411
34. Kahveci O, Belli S. Composite bond strength to intact enamel with current simplified adhesives. *J Adhes Dent.* 2011; 13(1):31-7. PMID:21403934
35. Cardoso PEC, Braga RR, Carrilho MRO. Evaluation of a microtensile, shear and tensile tests determining the bond strength of three adhesive systems. *Dent Mat.* 1999; 14(6):394-398. [https://doi.org/10.1016/S0300-5712\(99\)00012-3](https://doi.org/10.1016/S0300-5712(99)00012-3)
36. Pashley DH, Carvalho RM, Sano H, Nakajima M, Yoshiyama M, Shono Y, et al. The microtensile bond test: a review. *J Adhes Dent.* 1999; 1(4):299-309. PMID:11725659
37. Braga RR, Meira JB, Boaro LC, Xavier TA. Adhesion to tooth structure: a critical review of macro test methods. *Dent Mater.* 2010; 26(2):e38-49. <https://doi.org/10.1016/j.dental.2009.11.150> PMID:20004960